

## Dielectric properties of *Raphia* Fiber from *Epidermis* of young *Raphia Vinifera* leaflet

Sunday Edet Etuk<sup>1</sup>, Sunday Samuel Ekpo<sup>1</sup>, Ubong Williams Robert<sup>2</sup>, Okechukwu Ebuka Agbasi<sup>3,\*</sup>, Enwongo-Abasi Amos Effiong<sup>1</sup>

<sup>1</sup>Department of Physics, Faculty of Science, University of Uyo, P.M.B 1017, Uyo, 520003, Nigeria.

<sup>2</sup>Department of Physics, Faculty of Physical Sciences, Akwa Ibom State University, P.M.B 1167, Ikot Akpaden, Mkpat Enin, 52001, Nigeria.

<sup>3</sup>Department of Physics, College of Physical Science, Michael Okpara University of Agriculture, P.M.B. 7267, Umudike, 555, Nigeria.

\*e-mail: agbasi.okechukwu@gmail.com, +2347069547850

Submitted: 03/12/2021 Accepted: 02/05/2022 Published online: 06/05/2022

**Abstract:** There are materials that could serve useful purpose(s) in many fields, but they are left unutilized due to lack of both the knowledge on their useful properties and availability of values as per such properties. Notably, the knowledge of dielectric properties of some materials of plant origin is lacking whereas such is necessary for industrial, agricultural, electrical, electronics, biophysical and medical applications as well as other uses of a material. In this research, *Raphia Vinifera* is a material of choice. The experimental determination and computation of some dielectric properties of *Raphia* fiber from *epidemis* of young leaflets of *Raphia Vinifera* is explored. The properties considered for determination were dielectric permittivity, loss angle and dissipation factor. A Schering Bridge arrangement was employed, with a fixed thickness and varying areas of sample at various select frequencies. The values of the investigated properties recorded for our research sample trended towards being dependent of frequency. At frequency values above 1 kHz, the values of the properties determined decreased with increase in frequency. The values compared favorably with those of the already known and commonly used dielectric materials. The preliminary investigation showed that *Raphia Vinifera* would have usefulness in the electrical and electronic industries as raw material for the production of capacitor among other uses.

**Keywords:** Capacitance; Dielectric permittivity; Dissipation factor; Frequency, Loss angle

### I. INTRODUCTION

Dielectrics are a class of materials (insulators and high- $E_g$  semiconductors) that show polarization effects (separation of the centres of positive and negative charges) upon the application of an external electric field [1]. The dipole orientation and charge migration in broad frequency, temperature and pressure range can be examined via dielectric spectroscopy [2]. Knowledge upon the dielectric properties of materials can be utilized in several fields of science, engineering and industry including agriculture, biophysics, electronics and electrical industry, and medical applications [1, 2, 3, 4, 5]. The most important and frequently used frequency-dependent dielectric formalisms include though not limited to namely relative permittivity, impedance, ac conductivity and electric modulus [6]. The use of the appropriate formalism is decided depending on

the data and the electrical characteristics of the investigated materials. In recent times, the search for electrically-insulating materials has been of great concern with elaborate dielectric factors determining the behavior of such materials.

The use of new bioplastics, green polymers and plant-origin materials is a significant contribution towards a sustainable future [2, 7, 8]. This is achieved by employing economically attractive and environmentally friendly biodegradable materials to increase their disposability [8]. *Raphia vinifera* is commonly known as Bamboo palm while others commonly refer to it as the West African piassava palm, an evergreen tree growing to 6 m that is commonly found in Africa [9, 10]. It is a monocotyledon plant, characterized by solid unbranched trunks having fan-shaped pinnate leaves when fully matured [11, 12]. Each leaf is about twice as long as the stem and may contain as many as 80

to 100 leaflets. The soft silk-like fiber from the epidermis of the tender leaves of the *raphia* palm is an important fiber used locally for weaving of hats, mats, baskets, bags, ropes, and ceremonial costumes. *Raphia vinifera* belongs to the family called *Arecaceae* [13] and it is a native to Benin, Ghana, Nigeria, Gambia, Togo, Central African Republic, Democratic Republic of Congo, and Cameroun. With dielectric measurements, the molecular dynamics and structural behavior can be understood and contribute to the structure-property understanding for such materials [2].

In the present study, the dielectric properties of *raphia* fiber obtained from the epidermis of young leaves of the *Raphia vinifera* plant are presented at room temperature and in a frequency range of 0.10 to 100 kHz, a material that has not been investigated before dielectrically. The aim of this research is to provide data for plausible utilization of the fiber as dielectric material in electrical/electronic industry as well as other purposes it may be deemed fit based on its dielectric data. Since several fibers can be got from each leaf which is mostly discarded as waste, findings from this study will help to solve associated waste disposal problems while ensure sustainable development.


## II. MATERIALS AND METHOD

### 1. Materials

The young leaves of *raphia vinifera*, which were used in this work, were obtained from Ididep village in Ibiono Ibom Local Government Area of Akwa Ibom State, Nigeria. The young leaves were randomly selected and used in this study. The epidermis of the young leaflets were, on arrival in the laboratory, separated from other parts of the leaflets and immediately placed on a flat dry clean transparent glass plate holding the extreme ends with strong adhesive tape to the glass. It was kept very flat and firm on the glass surface to avoid folding itself and kinking when dry. Several epidermises were gotten from many young leaflets and treated using the same procedure applied in each case. The samples were allowed to remain in their positions on the glass plate at room temperature ranging between 27°C and 30°C (monitored with digital thermometer using type-K probe with sensor) for 21 days. This was necessary to allow for complete dryness before the samples were removed from the glass plate. **Fig. 1** shows the *Raphia* (bamboo) palm and also its fiber (when subjected to drying).


### 2. Procedure for measurement of dielectric properties of the *raphia* fiber

A parallel-plate capacitor method employing Schering Bridge [14, 15, 16] was used to determine the dielectric permittivity of the *raphia* fiber in this

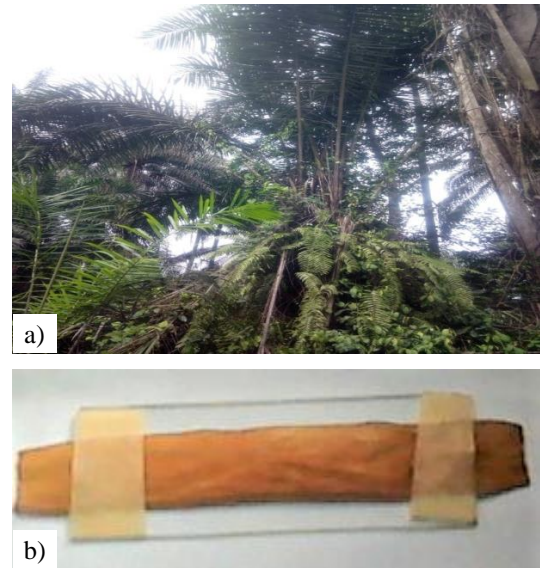

**Figure 1.** Photographs of (a) *Raphia vinifera* palm (b) the *raphia* fiber under drying

research work. The fiber was placed between two parallel copper plates, each measuring  $4.95 \cdot 10^{-4} \text{ m}^2$  in area, A to form a parallel-plate capacitor having electrical conducting leads attached to each plate at their outer surfaces. The formation was weighed down uniformly using a load of about 20N to leave the sandwiched *raphia* fiber with relatively no air gap between the fiber (employed as dielectric material) and the copper plates. Very importantly, care was taken to avoid direct contact between the two copper plates. A synthesized signal generator (Agilent 83732A) as AC source and a dual trace oscilloscope (Model CA620) as a display instrument to monitor the balance point were used with the Schering Bridge arrangement (**Fig. 2**).

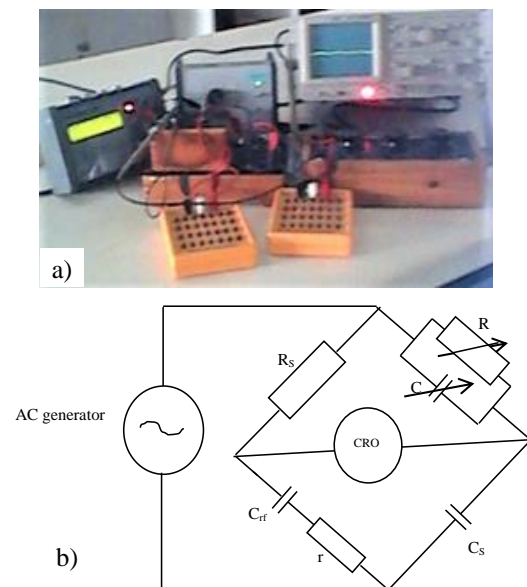

**Figure 2.** Setup of Schering Bridge used in the study (a) Experimental photo (b) Schematic diagram

The procedure was repeated for raphia fiber samples sandwiched between copper plates with areas measuring  $4.40 \cdot 10^{-4} \text{ m}^2$ ,  $3.63 \cdot 10^{-4} \text{ m}^2$ ,  $3.30 \cdot 10^{-4} \text{ m}^2$ , and  $2.75 \cdot 10^{-4} \text{ m}^2$  while the thickness,  $d$  of the raphia fiber sample remained fairly constant ( $d = 0.05 \text{ mm}$ ), measured with digital vernier calipers at several positions along the length with a mean value. The experimental data obtained were employed, to compute the capacitance, dissipation factor, and loss angle of the raphia fiber sample at varying frequencies from 0.10 to 100 kHz. The measurement in each case was taken five times after which the mean value was calculated and recorded.

The capacitance,  $C_{rf}$ , of the raphia vinifera young leaflet fiber was calculated at the balance point of the Schering Bridge, in each case, using the mathematical formula given by several authors including [16]

$$C_{rf} = \frac{RC_s}{R_s} \quad (1)$$

The leakage resistance,  $r$  of the capacitor arrangement under test was obtained by employing the mathematical relationship

$$r = \frac{CR_s}{C_s} \quad (2)$$

Dissipation factor,  $D$  in each case was computed using the equation

$$D = \omega C_{rf} r = \tan \phi \quad (3)$$

$R_s$  and  $R$  are select resistance values from decade resistance boxes,  $C_s$  and  $C$  are select capacitance values from decade capacitance boxes,  $\omega = 2\pi f$  (where  $f$  is the frequency of the applied AC signal),  $\phi$  is the loss angle. Dielectric loss is affected by the loss angle, and dielectric loss is an essential element of power factor [17, 18]. It is believed to be determined by the amount of current wave being  $90^\circ$  out of phase with voltage, a phenomenon known as dielectric loss angle.

By employing Origin software, the capacitance,  $C_{rf}$  values got at different frequencies versus the area,  $A$  were plotted for the raphia fibre investigated. The value of dielectric permittivity,  $\epsilon_{rf}$  was deduced from the slope of the graph making use of the mathematical relationship as expressed by several authors including [19, 20, 21, 22]

$$C_{rf} = \frac{\epsilon_0 \epsilon_{rf} A}{d} \quad (4)$$

where  $d$  is the common thickness of the raphia fiber,  $\epsilon_{rf}$  is the dielectric permittivity of the raphia fiber investigated,  $\epsilon_0$  is the relative permittivity of free space, which is  $8.854 \cdot 10^{-12} \text{ Fm}^{-1}$ .

By substituting for the actual values of  $d$  and  $\epsilon_0$  in equation (4), we have

$$C_{rf} = 1.7708 \cdot 10^{-7} \epsilon_{rf} A \quad (5)$$

Every measurement taken was at room temperature of  $(28 \pm 1)^\circ\text{C}$  and relative humidity of 50%. Dielectric constant, otherwise known as relative permittivity values for conventional dielectric materials (as reported) were tabulated for the purpose of comparing with the results of our investigation in this research.

### III. RESULTS, ANALYSIS AND DISCUSSION

The mean (with standard error) values of capacitance, loss angle, and dissipation factor at different frequencies deduced for the studied sample are shown in Table 1. It is evident in the expression that the capacitance of the sample decreases with increase in frequency.

Fig. 3 displays a linear relationship between the mean capacitance values and values of the sample's area at each frequency.


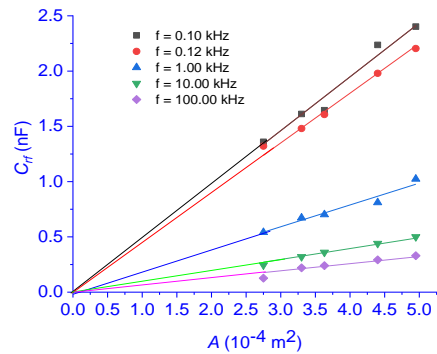


Figure 3. Variation of Capacitance with the sample's area

The values of dielectric permittivity were deduced from the slopes of the plots of mean capacitance at each frequency against area. The mean dielectric permittivity also decreases with increase in frequency. This is due to the fact that dipoles have less time (as the frequency progressively increases) to orient with the applied electric field resulting into decrease of real part of permittivity and hence the real part of capacitance. This is confirmed by equations (4) and (5). However, it has been observed that in some cases, dielectric permittivity values at frequencies below 1 kHz do not show significant variation from the values obtained at 1 kHz. This, essentially, means that there is no other dipolar relaxation process at a frequency below 1 kHz. As remarked by Halizan et al [23], good dielectric permittivity material has huge potential in capacitive energy storage devices for electronic applications. It can be clearly seen that loss angle values decrease with increase in frequency. The difference is very slight at frequency range below 1 kHz. It may not be wrong to aver that the value of loss angle is

approximately constant for our test sample at a frequency range below 1 kHz.

The loss angle varies with frequency for our test sample. Values for dissipation factor ( $\tan \phi$ ) recorded for sample in **Table 1** reveal decreasing trend with increase in applied frequency. However, the decrease seems to be infinitesimal within the frequency bracket below 1 kHz. This relationship is illustrated using a log- log representation as shown in **Fig. 4**.

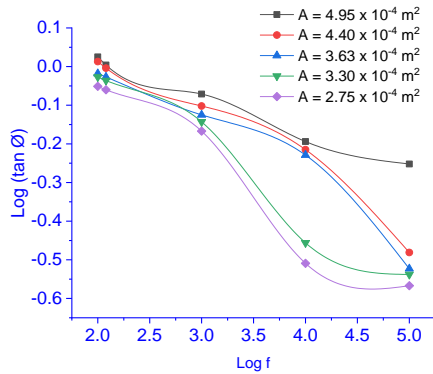


**Figure 4.** Log-log representation of dissipation factor versus frequency

Considering our research sample in terms of dissipation factor within the frequency range investigated, it is better at 100 kHz because the lower the dissipation factor, the better the dielectric is. Considering the trend, it is presumable that dissipation factor for this material will be lower at frequencies beyond 100 kHz, thus resulting in a better dielectric. The values of dielectric permittivity of our research sample at different frequencies are recorded in **Table 2**. It can be seen from the table that at the frequency of 1 kHz, the sample has a dielectric permittivity value of 11.14, but was greater at a lower frequency, thereby showing slight differences within the lower frequencies (below 1 kHz) bracket.

**Table 3** shows the dielectric constant values reported in the literature for some commonly used dielectric materials. A dielectric permittivity value of 5.57 is recorded for our research sample at the frequency of 10 kHz. This value is slightly greater than the reported values for Mica (Muscovite) as 5.4; Bakelite as 5.0; Pyrex glass 3320, 7040, 7052, 7060, 7070, 7740, 7750, 7760, being 4.71, 4.65, 4.77, 5.07, 4.70, 4.0, 5.0 – 5.1, 4.28 and 4.5 respectively [24, 26, 28, 29] as seen in **Table 3**. At the frequency of 100 kHz, our investigated sample recorded 3.64 as the dielectric permittivity. This value is about the value of dielectric constant reported for paper (3.5), paper (bond) as 3.0, Mylar (3.2), rubber (3.0 – 4.0), plexiglass (3.4), titanium dioxide (3.0 – 4.0), Sulphur (sublimed) as 3.69 and PVC (3.18). Comparing the

values of dielectric permittivity obtained for our chosen research sample within the radio frequency with the dielectric constant values of most of the commonly used dielectric materials as reported in the literature, it is correct to posit that our test sample exhibits a good and high ranking as a dielectric material. The manifestation of anomalous dielectric dispersion exhibited by our tests sample as clearly observed in **Fig. 5** has its support from the report of Vasudeva [24] and that of Salman [35] and Salman et al [36].

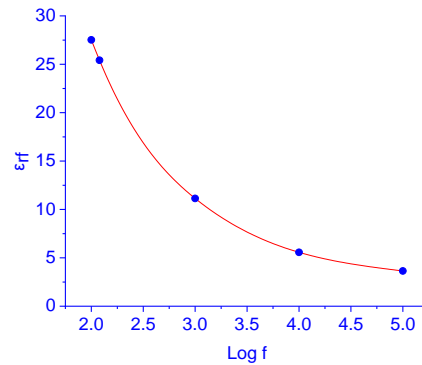

**Figure 5.** Sample's dielectric permittivity versus log of frequency

The value of dissipation factor obtained for the studied sample at the frequencies investigated follows the trend reported by Etuk et al [14] for some select eggshell membranes, which include those of eggs from Hen, Layers, Duck, Turkey, and Quail, which range between 0.173 and 0.350 at frequency of 100 kHz. It can be inferred that at frequency as high as 3 GHz, dissipation factor would also drop towards the range 0.002 to 0.005 even below as in the eggshell membrane. Values reported by Etuk et al [14] are approximately in the range reported by Fink and McKenzie [37] as (0.01 - 0.06), 0.04, (0.07 - 0.028) 0.0011, and (0.0011 - 0.0025) for cellulose acetate, nylon 6, nylon 10, hard rubber, and glass mica respectively.

**Table 1** Results of capacitance, loss angle, and dissipation factor determinations for the studied sample

$f$ (kHz)	$A = 4.95 \times 10^{-4} \text{ m}^2$			$A = 4.40 \times 10^{-4} \text{ m}^2$			$A = 3.63 \times 10^{-4} \text{ m}^2$			$A = 3.30 \times 10^{-4} \text{ m}^2$			$A = 2.75 \times 10^{-4} \text{ m}^2$		
	$C_{rf}$ (nF)	$\phi$ (°)	Tan $\phi$	$C_{rf}$ (nF)	$\phi$ (°)	Tan $\phi$	$C_{rf}$ (nF)	$\phi$ (°)	Tan $\phi$	$C_{rf}$ (nF)	$\phi$ (°)	Tan $\phi$	$C_{rf}$ (nF)	$\phi$ (°)	Tan $\phi$
0.10	2.402	46.90	1.069	2.237	45.92	1.033	1.646	44.10	0.969	1.612	43.46	0.948	1.360	41.86	0.896
	±	±	±	±	±	±	±	±	±	±	±	±	±	±	±
	0.006	0.32	0.012	0.001	0.04	0.002	0.003	0.06	0.002	0.001	0.02	0.001	0.003	0.10	0.003
0.12	2.204	45.46	1.016	1.980	44.94	0.998	1.607	43.34	0.944	1.480	42.80	0.926	1.321	41.12	0.873
	±	±	±	±	±	±	±	±	±	±	±	±	±	±	±
	0.003	0.04	0.001	0.004	0.06	0.002	0.002	0.06	0.010	0.002	0.06	0.002	0.001	0.02	0.001
1.00	1.024	40.56	0.856	0.811	38.52	0.796	0.702	37.18	0.759	0.672	36.10	0.729	0.541	34.32	0.683
	±	±	±	±	±	±	±	±	±	±	±	±	±	±	±
	0.002	0.12	0.004	0.004	0.16	0.005	0.002	0.08	0.002	0.002	0.12	0.003	0.002	0.06	0.001
10.00	0.500	32.68	0.642	0.440	31.76	0.619	0.360	30.62	0.592	0.320	19.62	0.356	0.245	17.48	0.315
	±	±	±	±	±	±	±	±	±	±	±	±	±	±	±
	0.002	0.06	0.001	0.002	0.08	0.002	0.002	0.08	0.002	0.003	0.16	0.003	0.001	0.04	0.001
100.00	0.330	29.34	0.562	0.292	18.50	0.335	0.240	17.14	0.309	0.220	16.26	0.292	0.127	15.20	0.272
	±	±	±	±	±	±	±	±	±	±	±	±	±	±	±
	0.002	0.10	0.002	0.001	0.04	0.001	0.001	0.08	0.007	0.001	0.06	0.001	0.001	0.08	0.001

**Table 2** Dielectric permittivity of the sample at different frequencies

Frequency, $f$ (kHz)	0.10	0.12	1.00	10.00	100.00
Dielectric permittivity, $\epsilon_{rf}$	27.52	25.42	11.14	5.57	3.64

**Table 3** Distinctive values of dielectric constant of some commonly used dielectric materials as reported in the literature [14, 24, 25 – 34]

Material	Dielectric	Material	Dielectric	Material	Dielectric
Rubber	3.0 – 4.0	Pyrex 7070	4.0	Polysulfones	3.13
Mylar	3.1	Pyrex 7720	4.5	Poly phenylene oxide	2.59
Bakelite	5.0	Pyrex 7740	5.0 - 5.1	Natural rubber	2.6
Paper (bond)	3.0	Pyrex 7750	4.28	Polychloroprene	6.6
Mica	3.0 – 8.0	Pyrex 7760	4.5	Polycrylonitrile	5.5
Paper	3.5	Vycor 7230	3.83	Glass bonded mica	6.3 – 9.3
Teflon	2.1	Vycor 7900	3.9	Soda lime glass	7.2
Air (1 atm)	1.00059 – 1.0006	Vycor 7910	3.8	Cordierite	4.02 – 6.23
Air (100 atm)	1.0548	Vycor 7911	3.8	Fluorocarbons	2.1 – 3.6
Vacuum	1.0	Germanium	16.0	Paraffin wax	2.0
Corning 8877	9.5	Porcelain	6.5	Poly vinylidene fluoride	12.2
Corning 0120	6.65	Plexiglass	3.4	Polymethyl methacrylate	3.12
Corning 0080	6.75	Polyethene	2.25 – 2.60	Polychlorotrifluoroethylene	2.65
Corning 0010	6.32	Polyvinyl chloride	3.18 – 5.3	Polybutadiene	2.5
Glass	5.0 – 10.0	G.E. Clear (Silica)	3.81	Sulphur (sublimed)	3.69 – 4.44
Mica (Canadian)	6.9 – 7.3	Quartz (Fused)	3.75	Polyceram 9606	5.57
Mica (Muscovite)	5.4 – 8.7	Titanium dioxide	3.0 – 4.0	Cellulose acetate	3.5 – 7.5
Pyrex 1710	6.0	Polypropylene	2.2	Alumina	8.0 – 10.0
Pyrex 3320	4.71	Neoprene	6.7 – 16.0	Polycarbonate	2.92
Pyrex 7040	4.65	ABC (Plastic)	2.4 – 3.8	Polyoxymethylene	3.8
Pyrex 7050	4.77	Barium titanate	5.0 - 450.0	Nylon 6 and nylon 10	3.5 – 3.6
Pyrex 7052	5.07	Forsterite	6.2 – 6.5	Borosilicate	4.1 – 4.9
Pyrex 7060	4.7	Hard rubber	2.95 – 4.80	Boron nitride	4.15

#### IV. CONCLUSION

The dielectric permittivity of a material used for separating conductive plates of a capacitor determines the amount of energy that a capacitor can store when voltage is applied. A measure of loss-rate of energy known as dissipation factor of a dielectric material is another determining factor. This factor represents the tangent of the measure of current wave deviation from being 90° out of phase with voltage, designated loss angle.

The values of dielectric permittivity obtained for our study sample (*Raphia* fiber from epidermis of young *Raphia vinifera* leaflet) in comparison with dielectric constant values of several already known and commonly used dielectric materials makes our investigated sample an alternative material of choice as dielectric material. The values obtained for the studied parameters give a very strong suggestion that the *Raphia* fiber is a potential raw material for capacitor fabrication. *Raphia vinifera* young leaflet epidermis fiber is a biological membrane, though of plant kingdom. It grows well along creeks. The material is environmentally friendly and sustainable. Based on the afore-stated findings, it is highly recommended for electrical/electronic industry utilization. For future research, the influence of temperature on the investigated properties could be examined.

#### REFERENCES

- [1] Bonard S, Moreno-Serna V, Kortaberria G, Díaz Díaz D, Leiva A, Saldías C, Dipolar Glass Polymers Containing Polarizable Groups as Dielectric Materials for Energy Storage Applications. A Mini review. *Polymers* 11 (2) (2019) 317.  
<https://doi.org/10.3390/polym11020317>
- [2] Soccio M, Martínez-Tong DE, Guidotti G, Robles-Hernández B, Munari A, Lotti N, Alegria A, Broadband Dielectric Spectroscopy Study of Biobased Poly(alkylene 2,5-furanoate)s' Molecular Dynamics. *Polymers* 12 (6) (2020) 1355.  
<https://doi.org/10.3390/polym12061355>
- [3] Bojovschi A, Quoc T, Trung H, Quang D, Le T, Environmental Effects on HV Dielectric Materials and Related Sensing Technologies. *Applied Sciences* 9 (5) (2019) 856.  
<https://doi.org/10.3390/app905085>
- [4] Barber P, Balasubramanian S, Anguchamy Y, Gong S, Wibowo A, Gao H, Zur Loye HC, Polymer Composite and Nanocomposite Dielectric Materials for Pulse Power Energy Storage. *Materials* 2 (4) (2009) pp. 1697–1733.  
<https://doi.org/10.3390/ma2041697>
- [5] Oliveira JGD, Pinto ENMG, Silva Neto VP, D'Assunção AG CSRR-Based Microwave

#### AUTHOR CONTRIBUTIONS

**S.E. Etuk:** Conceptualization, Supervision, Writing – Original draft, review and editing.

**S.S. Ekpo:** Resources, Data curation, Writing - Review and editing.

**U.W. Robert:** Methodology, Investigation, Writing – Original draft, review and editing.

**O.E. Agbasi:** Visualization, Resources, Writing - Review and editing.

**E.A. Effiong:** Resources, Writing - Review and editing.

#### DISCLOSURE STATEMENT

We have no conflict of interest to declare.

#### ORCID

**S.E. Etuk** <https://orcid.org/0000-0002-2573-8314>

**S.S. Ekpo** <https://orcid.org/0000-0002-9361-7186>

**U.W. Robert** <https://orcid.org/0000-0001-9979-7176>

**O. E. Agbasi** <https://orcid.org/0000-0001-5649-0107>

Sensor for Dielectric Materials Characterization Applied to Soil Water Content Determination. *Sensors* 20 (1) (2020) 255.  
<https://doi.org/10.3390/s20010255>

- [6] Dyre JC, The random free-energy barrier model for ac conduction in disordered solids. *Journal of Applied Physics* 64 (5) (1988) pp. 2456–2468.  
<https://doi.org/10.1063/1.341681>

- [7] Tuan Naiwi T, Aung M, Ahmad A, Rayung M, Su'ait M, Yusof N, Wynn Lae K, Enhancement of Plasticizing Effect on Bio-Based Polyurethane Acrylate Solid Polymer Electrolyte and Its Properties. *Polymers* 10 (10) (2018) 1142.  
<https://doi.org/10.3390/polym10101142>

- [8] Avella M, Buzarovska A, Errico M, Gentile G, Grozdanov A, Eco-Challenges of Bio-Based Polymer Composites. *Materials* 2 (3) (2009) pp. 911–925.  
<https://doi.org/10.3390/ma2030911>

- [9] Etukudo I, Forest Our Divine Treasure, Dorand Publishers, Uyo, 2000.

- [10] Van Wyk B, and Gericke N, People's Plants. A Guide to Useful Plants of Southern Africa, Briza Publications, Pretoria (2000) p. 352.

- [11] Etuk SE, Akpabio LE, and Akpabio KE, Investigation of *Raphia hookeri* Trunk as a potential ceiling material for passively-cooled building design, Ghana J Sci. 43 (37) (2003).
- [12] Child R, Coconut, 2<sup>nd</sup> edn., Longman, Harlow. 1974.
- [13] Faba-Tendo J, Etape EP, Krause RWM, Namondo BV, Potential of blended biomass feedstock from species of raffia palm (*Raffia farinifera*, *Raffia hookeri*, and *Raffia vinifera*) and oil Palm Empty Fruit Bunch OPEFB from Cameroon. African Journal of Pure and Applied Chemistry 12 (4) (2018) pp. 25 – 33.
- [14] Etuk SE, Robert UW, Emah JB, and Agbasi OE, Dielectric Properties of Eggshell membrane of some select Bird species, Arabian Journal for Science and Engineering (2020) <https://doi.org/10.1007/s13369-020-04931-7>
- [15] Menkiti AI, Ifedili SO, Uwah EJ, Abumere OE, Awate IO, Advanced Practical Physics Manual, Nigerian University Physics Series, Spectrum Books Ltd (2010) p. 237.
- [16] Anand MMS, Electronics Instruments and Instrumentation Technology, 7<sup>th</sup> edn., Ghosh K. Ghosh, New Delhi, 2009.
- [17] Thereja BL, and Thereja AK, A Textbook of Electrical Technology, S. Chand, New Delhi (2000) p. 530.
- [18] Sawhney AK, and Sawhney PA, A Course in Electrical and Electronic Measurements and Instrumentation, 19<sup>th</sup> edn., Gagan Kapur Dhampat Rai and Co (P) Ltd, Delhi (2011) pp. 170 – 172.
- [19] Robertson CR, Fundamental Electrical and Electronic Principles, 3<sup>rd</sup> edn., Newnes, Elsevier, Amsterdam, (2008) pp. 101 – 102.
- [20] Etuk SE, Akpabio LE, and Ekpe SD, Verification of Relationship between Relative Permittivity and Viscosity for determination of Adulteration and Grades of Engine Oil Samples, Global Journal of Pure and Applied Science 7 (3) (2001) pp. 579 – 584. <https://doi.org/10.4314/gjpas.v7i3.16291>
- [21] Mee C, Grundell M, Arnold B, Brown W, International A/AS Level Physics, Endorsed by University of Cambridge International examinations, Hodder Education, Hachette Livre, UK (2011) pp. 295 – 296.
- [22] Morris NM, Mastering electronic and Electrical Calculations, Macmillan, Hong Kong (1996) p. 8.
- [23] Halizan MZM, Mohamed Z, Yahya AK, Understanding the structural, optical, and dielectric characteristics of SrLaLiTe1-xMnxO6 perovskites, Scientific Reports 11 (2021) 9744. <https://doi.org/10.1038/s41598-021-89132-4>
- [24] Vasudeva AS, Modern Engineering Physics, 6<sup>th</sup> Edn., S. Chan & Co. Ltd, New Delhi, Part V, Chapter 4 (2013) pp. 63 – 83.
- [25] Thereja BL, Basic Electronics-Solid State, 1<sup>st</sup> Multicolor Illustration edn., S. Chand & Company Ltd, Ram Nagar (2008) p. 63.
- [26] Sears FW, Zemansky MW, Young HD, University Physics, 6<sup>th</sup> edn. Addison Wesley, 1982.
- [27] Young HD, Freeman RA, and Ford AI, University Physics with Modern Physics, 12<sup>th</sup> edn., SEARS and ZEMANSKY'S Pearson Addison Wesley, San Francisco (2008) pp. 828 – 829.
- [28] Frederikse HPR, Dielectric constant of glass in CRC 12, CRC Press LLC (2000) pp. 48 - 58
- [29] Lide DR, CRC Handbook of Chemistry and Physics, 8<sup>th</sup> edn., CRC Baco Raton (2005) pp.12–51.
- [30] Anderson HL, A Physicist's Desk Reference, American Institute of Physics, New York, 1989.
- [31] Brandup J, and Immergut EH, Polymer Handbook, 3<sup>rd</sup> edn., Wiley, Hoboken, 1989.
- [32] Nelkon M, and Parker P, Advanced Level Physics, 5<sup>th</sup> edn., Heinemann Educational books Ltd, London (1982) p. 603.
- [33] Young HD, and Federikse HPR, Compilation of the static dielectric constant of inorganic solids, J Phys Chem Ref. Data 2 (1973) p. 313. <https://doi.org/10.1063/1.3253121>
- [34] Gray DE, American Institute of Physics Handbook, 3<sup>rd</sup> edn., McGraw-Hill, New York (1972) pp. 5 - 132.
- [35] Salman F, AC Conductivity and Dielectric Study of chalcogenide glasses of Se-Te-Ge, Turk J Phys. 28 (1) (2004) pp. 41 – 48.
- [36] Salman F, Aboelhssan S, Sheha E, Elmansy MK, Dielectric Properties and Conductivity of KHCO<sub>3</sub>, Turk J Phys. 28 (1) (2004) pp. 57 – 63.
- [37] Fink DG, and McKeenzie AA, Electronics Engineers' Handbook. McGraw-Hill Books, New York (1975) pp. 6 – 36.



This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution NonCommercial (CC BY-NC 4.0) license.